

^{75}As NMR Study of Hole-Doped Superconductor $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ ($T_c \simeq 38$ K)

Hideto Fukazawa^{1,2*}, Takehiro Yamazaki¹, Kenji Kondo¹, Yoh Kohori^{1,2}, Nao Takeshita^{2,3},
Parasharam M. Shirage³, Kunihiro Kihou³, Kiichi Miyazawa^{3,4}, Hijiri Kito^{2,3}, Hiroshi Eisaki^{2,3}, and Akira Iyo^{2,3}

¹*Department of Physics, Chiba University, Chiba 263-8522, Japan*

²*JST, TRIP, Chiyoda-ku, Tokyo 102-0075, Japan*

³*National Institute of Advanced Industrial Science and Technology, Tsukuba 305-8562, Japan*

⁴*Department of Applied Electronics, Tokyo University of Science, Noda 278-8510, Japan*

(Received February 2, 2009)

We report the ^{75}As nuclear magnetic resonance (NMR) measurement of the hole-doped superconductor $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ with different lattice parameters and different superconducting volume fractions ($T_c \simeq 38$ K). ^{75}As -NMR spectra revealed that the magnetically ordered and superconducting phases are microscopically separated. The spin-lattice relaxation rate $1/T_1$ in the normal state reflects the existence of a large two-dimensional antiferromagnetic spin fluctuation. The $1/T_1$ in the superconducting state down to the lowest measurement temperature T varies close to T^3 . In addition, it exhibits no coherence peak just below T_c . This shows a T dependence similar to those of other iron pnictides.

KEYWORDS: $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$, superconductivity, magnetic order, phase separation, nuclear magnetic resonance

The discovery of superconductivity in F-doped LaFeAsO with a superconducting transition temperature $T_c = 26$ K¹⁾ has accelerated further investigations of related superconductors.²⁻⁹⁾ The $3d$ electrons originating from an FeAs layer form multiple bands at the Fermi level and play an important role in superconductivity.^{10,11)} In particular, nondoped materials commonly exhibit an antiferromagnetic (AF) order with an adjacent structural phase transition, which resembles the parent materials of high- T_c cuprates. Hence, the relation between magnetic order and superconductivity is one of the vital issues in the investigations of such compounds.

K-doped BaFe_2As_2 is the firstly reported oxygen-free iron-pnictide superconductor with $T_c = 38$ K.⁶⁾ The crystal structure of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ is of the ThCr_2Si_2 -type. This structure possesses an FeAs layer similar to that realized in LaFeAsO . The parent material BaFe_2As_2 exhibits AF anomaly at $T_N = 140$ K.¹²⁾ Neutron diffraction measurements revealed an ordered moment of $0.87 \mu_B$ (Bohr magneton) at the Fe site with a q vector of $(1, 0, 1)$ for the orthorhombic structure.¹³⁾ It is important to note that this compound exhibits structural phase transition as well as AF anomaly.^{12,13)} The zero-field ^{75}As -NMR spectrum also revealed that the magnetically ordered state of this compound is commensurate.^{14,15)} The evaluated H_{int} at 4.2 K decreases gradually with increasing pressure.¹⁶⁾ The results are consistent with the other group's NMR results obtained using single crystals.¹⁷⁾

Several groups reported the phase diagram of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$.^{18,19)} For the compound, the AF anomaly disappears and superconductivity is induced by hole doping, K substitution for Ba. The superconducting (SC) state is confirmed to be the bulk from the specific heat jump at T_c .²⁰⁾ The most striking feature of the phase diagram is that the SC region widely spreads for $0.2 \leq x \leq 1$ and thus the possibility of the coexistence

of the AF and SC states exists for $0.2 \leq x \leq 0.4$. Bulk measurements cannot determine whether or not this coexistence is macroscopic. Hence, measurements with a local probe are strongly required. Recent μSR measurements show the existence of the phase-separated AF and SC states.^{21,22)} Here, we report the ^{75}As -NMR measurements of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ with different lattice parameters and different superconducting volume fractions ($T_c \simeq 38$ K) in order to investigate the gap symmetry of superconductivity and establish the nature of the coexistence of the AF and SC states.

To date, intensive NMR studies are performed on other iron pnictide superconductors.²³⁻²⁹⁾ Knight shift measurements revealed that the spin-singlet superconductivity is realized. The common feature of $1/T_1$ in the SC state is the T^3 behavior at low temperatures without T linear behavior, which indicates the absence of the residual density of states. This is apparently ascribable to the spin-singlet superconductivity with a nodal structure: d -wave superconductivity. However, the results of other experimental techniques suggest the fully gapped superconductivity: s -wave superconductivity.^{20,30,31)} Nagai *et al.* calculated $1/T_1$ and showed that the anisotropic $s_{\pm}$ -wave pairing, in which the sign of the SC order parameter changes between Fermi surfaces, explains the apparently controversial experimental results.³²⁾ To the best of our knowledge, this is the first report on the NMR study of hole-doped Fe-based superconductor.

Polycrystalline $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ samples were synthesized by a high-pressure method.²⁾ X-ray diffraction analysis revealed that the obtained samples have different lattice parameters, which is associated with the temperature control or the starting ratio of (Ba, K) and FeAs. In this study we used two different batches of samples and fixed the ratio of starting Ba to K at 0.6:0.4: $a = 3.923 \text{ \AA}$, $c = 13.220 \text{ \AA}$ sample and $a = 3.926 \text{ \AA}$, $c = 13.297 \text{ \AA}$ sample. According to the relation between the lattice parameter and the nominal composition x ,¹⁸⁾ the

* E-mail address: hideto@nmr.s.chiba-u.ac.jp

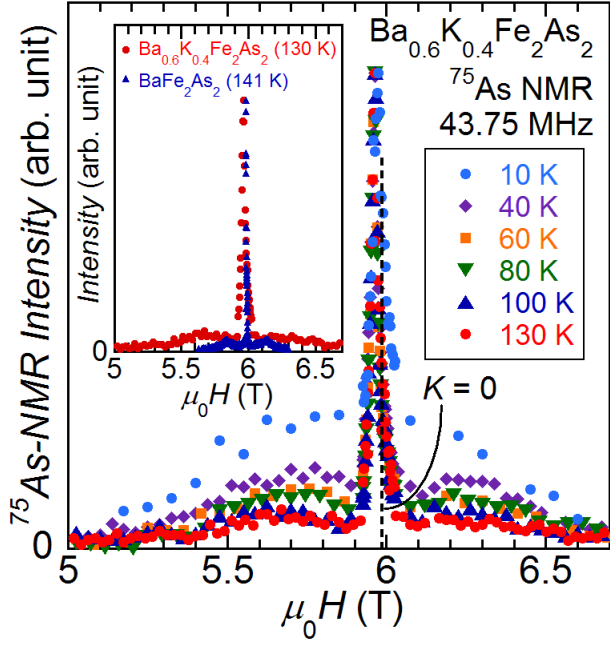


Fig. 1. (Color online) ^{75}As NMR spectra of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ at various temperatures. The inset shows the ^{75}As NMR spectra of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ and BaFe_2As_2 in the paramagnetic state.

materials correspond to $x = 0.3$ and 0.4 . For convenience, we utilize these x 's hereafter in this paper. Although the $x = 0.3$ sample was confirmed to be of nearly single phase by X-ray diffraction analysis, the $x = 0.4$ sample contained less than 10% FeAs impurity. We also determined the T_c and SC volume fraction of the samples with a commercial SQUID magnetometer. The T_c 's of the samples are about 38 K and the volume fractions for $x = 0.3$ and 0.4 are 75% and 50%, respectively. The NMR experiment on the ^{75}As nucleus ($I = 3/2$, $\gamma = 7.292 \text{ MHz/T}$) was carried out using phase-coherent pulsed NMR spectrometers and a superconducting magnet. We performed NMR measurement at around 6 T. According to the report on the upper critical field of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$,^{33,34)} the T_c ($\sim 6 \text{ T}$) is 35 K for the samples of $T_c(0 \text{ T}) = 38 \text{ K}$. The samples were crushed into powder for use in the experiments. The powder was oriented at 150 K at a field of 6 T. The c -axis of each microcrystal in oriented powders is perpendicular to the external field.¹⁴⁾ The NMR spectra were measured by sweeping the applied fields at a constant resonance frequency. The origin of the Knight shift $K = 0$ of the ^{75}As nucleus was determined by the ^{75}As NMR measurement of GaAs .³⁵⁾ T_1 was evaluated by a saturation recovery method.

In Fig. 1, we show the ^{75}As -NMR spectra of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ at various T 's. Even at higher temperatures, the spectra have broad satellite components in addition to the sharp center line at around 6 T. Because K is expected to locate randomly at the (Ba, K) site in $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$, these broad satellite components arise from the inhomogeneous distribution of the electric field gradient (EFG) at the As site. In the inset of Fig. 1, we show a comparison of the ^{75}As -NMR spectra of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ and BaFe_2As_2 in the paramagnetic state. The center line of the spectrum of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$

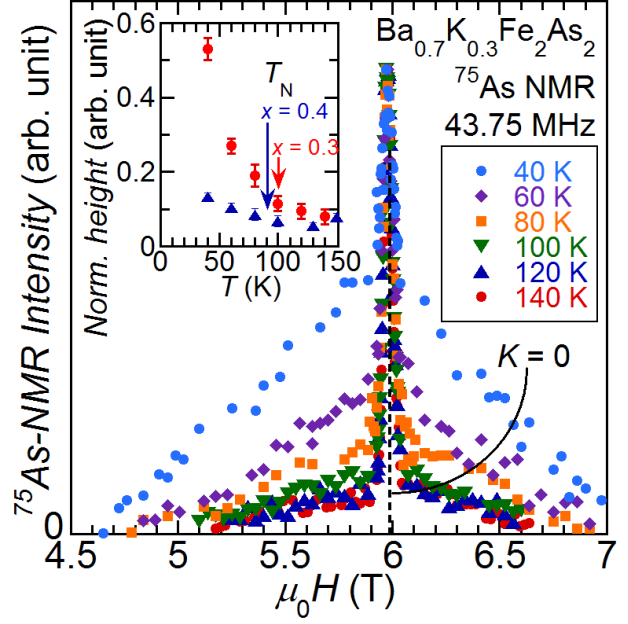


Fig. 2. (Color online) ^{75}As NMR spectra of $\text{Ba}_{0.7}\text{K}_{0.3}\text{Fe}_2\text{As}_2$ at various temperatures. The inset shows the T dependence of the normalized broad-satellite height against the center-line height in the spectra for $x = 0.3, 0.4$.

is broader than that of BaFe_2As_2 , which is also ascribable to the inhomogeneous distribution of the EFG at the As site and Knight shift. Since the EFG at the As site is expected to be parallel to the crystal c -axis and thus perpendicular to the external field, the ν_Q of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ is estimated to distribute at around 5 MHz, which is twice larger than the ν_Q of BaFe_2As_2 . The intensity of broad satellite components increases below approximately 80-100 K. This is attributable to the AF ordering below $T_N = 80\text{-}100 \text{ K}$. We will discuss the determination of T_N later. However, T_N is clearly larger than 80 K. Hence, this increase in intensity is hardly attributed to the impurity FeAs , which exhibits AF ordering below 77 K.³⁶⁾ Note that the center line observed in the paramagnetic (PM) state coexists even at 10 K with the magnetically ordered component. This indicates the occurrence of the phase separation of the AF and PM states at low temperatures, which is consistent with the results of μSR measurements.^{21,22)}

In Fig. 2, we show the ^{75}As -NMR spectra of $\text{Ba}_{0.7}\text{K}_{0.3}\text{Fe}_2\text{As}_2$ at various T 's. The increase in the intensity of the NMR signals of the satellite components is also observed and is much larger than that of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$. In the inset of Fig. 2, we plotted the T dependence of normalized broad-satellite height against center-line height for $\text{Ba}_{0.7}\text{K}_{0.3}\text{Fe}_2\text{As}_2$ and $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ in order to estimate AF transition temperature. We found that the transition temperature is approximately 100 K for $x = 0.3$. The temperature is roughly estimated to be between 80 and 100 K for $x = 0.4$. Hence, AF transition temperature decreases with increasing x . This is consistent with the macroscopic experimental results of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$.^{18,19)} It is difficult to accurately determine T_N for $x = 0.4$ since the signal intensity of broader satellites for $x = 0.4$ is

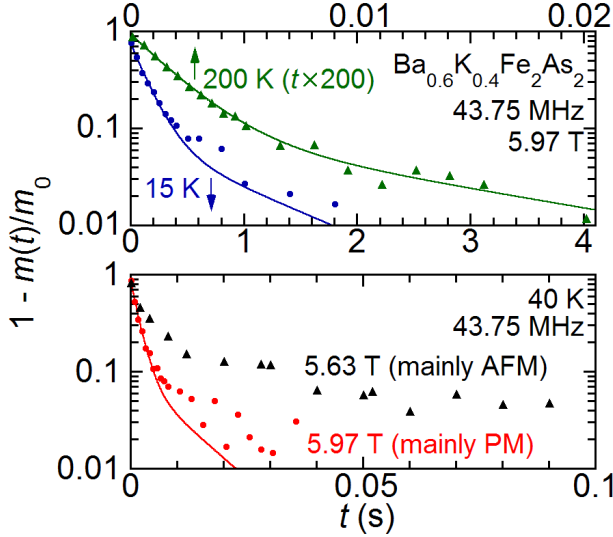


Fig. 3. (Color online) Nuclear magnetization recovery curves of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ at 15, 40, and 200 K. Solid lines denote the fitting curve using the formula written in the text.

much less than that for $x = 0.3$. We performed magnetization measurement above T_c , in order to determine AF transition temperature more accurately. However, we could not determine T_N because a small amount of ferromagnetic Fe impurity, which is not detected by X-ray diffraction analysis, masks the anomaly associated with T_N .

We additionally performed zero-external-field NMR measurements at 1.5 K and obtained spectra for $x = 0.3$ and 0.4 (not shown data). The obtained spectral profiles are basically the same as that of the parent material BaFe_2As_2 .^{14,15)} By the same analytical procedure described in ref. 15, we evaluated the internal magnetic field H_{int} at the As site to be 1.23(5) T for $x = 0.3$ and 1.17(3) T for $x = 0.4$. These values are rather smaller than $H_{\text{int}} = 1.39(2)$ T in BaFe_2As_2 ¹⁴⁾ and decrease with x . Since the magnetic transition temperature is a rough measure of the magnetic order parameter, this tendency of H_{int} with x is consistent with the smaller T_N of these compounds than that of BaFe_2As_2 . Furthermore, we note that there is no consistency between the fraction in the AF region and the SC volume fraction of the samples with x . At the present stage, we cannot explain this inconsistency. The K distribution in the samples might be related to the AF or SC fraction since the temperature control condition or the starting ratio of (Ba, K) and FeAs may affect such a local distribution of K. However, we cannot answer how K distributes in the AF and SC phases and can only state that the samples studied here have identical T_c 's.

In Fig. 3, we show nuclear magnetization recovery curves of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ at 15, 40, 200 K. We obtained T_1 at a fixed frequency of 43.75 MHz with an external field of 5.97 T in the T range of 4.2–250 K. The nuclear magnetization recovery curve was fitted by the following double-exponential function as expected for the center line of the spectrum of the nuclear spin $I = 3/2$ of the

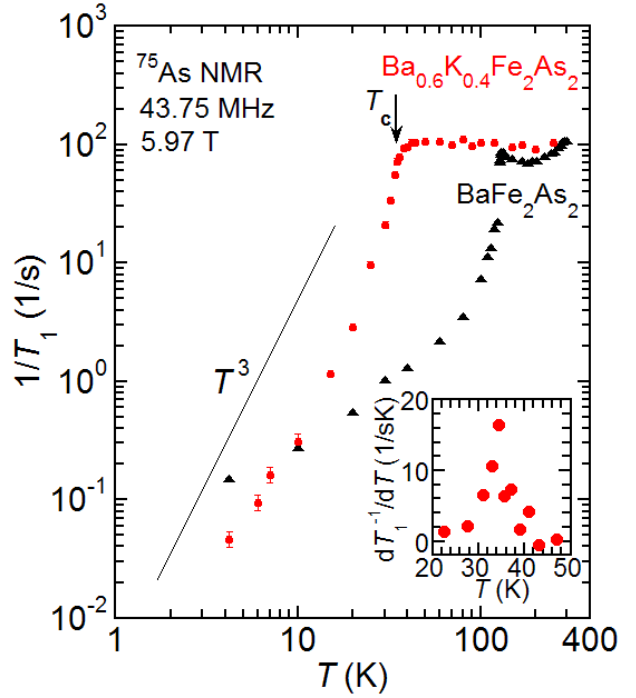


Fig. 4. (Color online) $1/T_1$'s of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ and BaFe_2As_2 . The solid line proportional to T^3 is a visual guide. The inset shows the derivative of $1/T_1$ of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$.

⁷⁵As nucleus,³⁷⁾

$$1 - \frac{m(t)}{m_0} = 0.1 \exp\left(-\frac{t}{T_1}\right) + 0.9 \exp\left(-\frac{6t}{T_1}\right),$$

where $m(t)$ and m_0 are nuclear magnetizations after a time t from the NMR saturation pulse and thermal equilibrium magnetization. In the paramagnetic state, the data are well fitted to the curve with a single T_1 component, as clearly seen in the result at 200 K. However, the data are less fitted with a single T_1 component below about 100 K. As shown in the data at 15 and 40 K, a deviation of the fitting curve from the experimental data exists and a longer T_1 component appears in the recovery curves. This is because the signals at around 5.97 T include signals from the nucleus affected by the AF-ordered state below about 80–100 K, which has a longer T_1 component. This is very clear in the data obtained at 5.63 T, at which the signals mainly come from the AF-ordered state. Therefore, a shorter T_1 component is an intrinsic relaxation rate for the center line of the spectrum at around 6 T. We tentatively analyzed the recovery curves with double T_1 components. However, we could not obtain a systematic T dependence of T_1 since a longer T_1 component has worse statistical accuracy than a shorter component. Single T_1 component fitting analysis, which is used to study a shorter T_1 component, has a systematic T dependence. Hence, we used single T_1 component fitting analysis for all T .

In Fig. 4, we show the T dependence of $1/T_1$ of ⁷⁵As of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ and BaFe_2As_2 . $1/T_1$ remains nearly constant above about 40 K in $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$, which indicates that the two-dimensional AF spin fluctuation of an itinerant electron system³⁸⁾ is predominant in this ma-

material. Assuming that $1/T_1T$ is proportional to a Curie-Weiss-like T dependence $1/(T + \theta_{CW})$ due to AF fluctuation in the T range between 40 and 250 K, we obtained the Curie-Weiss temperature $\theta_{CW} = -2(2)$ K. This should be interpreted to indicate that the normal and PM states of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ are on the verge of AF instability. This T dependence is quite different from that of an electron-doped system³⁹⁾ $\text{BaFe}_{1.8}\text{Co}_{0.2}\text{As}_2$,²⁸⁾ where the Korrington behavior and a pseudogap-like T behavior at higher temperatures are observed, and is similar to that of $\text{LaFeAsO}_{0.96}\text{F}_{0.04}$.²³⁾ Since the quantity of the substitution of K for Ba is much larger than that of Co for Fe, this result indicates that $3d$ electronic spin fluctuations are not markedly suppressed by K substitution, that is, by hole doping. Moreover, note that the normal state property of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ is similar to that of underdoped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$.⁴⁰⁾ Furthermore, the result is consistent with that of the theoretical study of $1/T_1$ on the basis of fluctuation-exchange approximation, which explains the presence and absence of the pseudogap behavior in the T dependence of $1/T_1$ of electron-doped and hole-doped iron-pnictide superconductors, respectively.⁴¹⁾

In the inset of Fig. 4, we show the derivative of $1/T_1$ of $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$. The sharp peak at around 35 K corresponds to the SC transition at a magnetic field of about 6 T. Below $T_c(5.97 \text{ T}) \simeq 35 \text{ K}$, $1/T_1$ rapidly decreases on cooling without a coherence peak. At lower temperatures, $1/T_1$ varies close to T^3 and is not exponential; the fitting of $1/T_1$ below 20 K is proportional to $T^{2.6(3)}$. In addition, no T linear behavior was observed down to the lowest measurement temperature of 4.2 K. This tendency of $1/T_1$ in the SC state is similar to the results commonly reported for other iron pnictides.^{23–26, 28, 29)} For $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$, specific heat²⁰⁾ and ARPES³¹⁾ measurements suggest a fully gapped superconductivity. At the present stage, we cannot exclude the possibility of unconventional superconductivity with a nodal structure. However, one of the possible explanations is the anisotropic $s_{\pm}$ -wave pairing model.³²⁾ In order to determine the detailed SC gap, direction-sensitive experiments such as specific heat and thermal conductivity measurements under accurate magnetic field are strongly required.

In summary, we performed the ^{75}As nuclear magnetic resonance (NMR) measurement of the hole-doped superconductor $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ with different lattice parameters and different superconducting volume fractions ($T_c \simeq 38 \text{ K}$). ^{75}As -NMR spectra revealed that the magnetically ordered and SC phases are microscopically separated. The spin-lattice relaxation rate $1/T_1$ in the nor-

mal state reflects the existence of a large two-dimensional AF spin fluctuation. The $1/T_1$ in the SC state down to the lowest measurement temperature T varies close to T^3 . In addition, it exhibits no coherence peak just below T_c . This shows a T dependence similar to those of other iron pnictides. Further studies including those of sample dependence are required to understand the origin of the high T_c in this category of iron-based superconductors; such studies are in progress.

The authors thank T. Saito and Y. Yamada for their contribution to this work. They also thank H. Ikeda for valuable discussion. This work is supported by a Grant-in-Aid for Scientific Research from the MEXT, Global COE program, AGSST of Chiba University.

- 1) Y. Kamihara *et al.*: J. Am. Chem. Soc. **130** (2008) 3296.
- 2) H. Kito *et al.*: J. Phys. Soc. Jpn. **77** (2008) 063707.
- 3) Z. A. Ren *et al.*: Euro. Phys. Lett. **82** (2008) 57002.
- 4) G. F. Chen *et al.*: Phys. Rev. Lett. **100** (2008) 247002.
- 5) X. H. Chen *et al.*: Nature **453** (2008) 761.
- 6) M. Rotter *et al.*: Phys. Rev. Lett. **101** (2008) 107006.
- 7) F. C. Hsu *et al.*: Proc. Natl. Acad. Sci. U.S.A **105** (2008) 14262.
- 8) X. C. Wang *et al.*: arXiv:0806.4688.
- 9) S. Matsuishi *et al.*: J. Am. Chem. Soc. **130** (2008) 14428.
- 10) I. I. Mazin *et al.*: Phys. Rev. Lett. **101** (2008) 057003.
- 11) K. Kuroki *et al.*: Phys. Rev. Lett. **101** (2008) 087004.
- 12) M. Rotter *et al.*: Phys. Rev. B **78** (2008) 020503(R).
- 13) Q. Huang *et al.*: Phys. Rev. Lett. **101** (2008) 257003.
- 14) H. Fukazawa *et al.*: J. Phys. Soc. Jpn. **77** (2008) 093706.
- 15) H. Fukazawa *et al.*: J. Phys. Soc. Jpn. **77** (2008) Suppl. C 138.
- 16) H. Fukazawa *et al.*: J. Phys. Soc. Jpn. **77** (2008) 105004.
- 17) K. Kitagawa *et al.*: J. Phys. Soc. Jpn. **77** (2008) 114709.
- 18) M. Rotter *et al.*: Angew. Chem. Int. Ed. **47** (2008) 7949.
- 19) H. Chen *et al.*: Euro. Phys. Lett. **85** (2009) 17006.
- 20) G. Mu *et al.*: arXiv: 0812.1188.
- 21) T. Goko *et al.*: arXiv: 0808.1425.
- 22) J. T. Park *et al.*: arXiv: 0811.2224.
- 23) Y. Nakai *et al.*: J. Phys. Soc. Jpn. **77** (2008) 073701.
- 24) K. Matano *et al.*: Euro. Phys. Lett. **83** (2008) 57001.
- 25) H.-J. Grafe *et al.*: Phys. Rev. Lett. **101** (2008) 047003.
- 26) H. Mukuda *et al.*: J. Phys. Soc. Jpn. **77** (2008) 093704.
- 27) A. Kawabata *et al.*: J. Phys. Soc. Jpn. **77** (2008) 103704.
- 28) F. Ning *et al.*: J. Phys. Soc. Jpn. **77** (2008) 103705.
- 29) H. Kotegawa *et al.*: J. Phys. Soc. Jpn. **77** (2008) 113703.
- 30) K. Hashimoto *et al.*: Phys. Rev. Lett. **102** (2009) 017002.
- 31) K. Nakayama *et al.*: arXiv: 0812.0663.
- 32) Y. Nagai *et al.*: New J. Phys. **10** (2008) 103026.
- 33) N. Ni *et al.*: Phys. Rev. B **78** (2008) 014507.
- 34) Z. S. Wang *et al.*: Phys. Rev. B **78** (2008) 140501(R).
- 35) T. J. Bastow: J. Phys.: Condens. Matter **11** (1999) 569.
- 36) K. Selte *et al.*: Acta Chem. Scand. **26** (1972) 3101.
- 37) W. W. Simmons *et al.*: Rhys. Rev. **127** (1962) 1168.
- 38) T. Moriya: J. Mag. Mag. Mater. **100** (1991) 261.
- 39) Y. Sekiba *et al.*: arXiv:0812.4111.
- 40) K. Ohsugi *et al.*: J. Phys. Soc. Jpn. **60** (1991) 2351.
- 41) H. Ikeda: J. Phys. Soc. Jpn. **77** (2008) 123707.